

# forAM® CP-Ti G1/G2 15-53 EG

Commercially pure Ti powder for additive manufacturing

#### **General material description**

Höganäs for AM CP-Ti G1/G2 EG is highly spherical powder for additive manufacturing. Commercially pure Ti has good strength to weight ratio combined with high elongation. It possess high corrosion resistance, very good cryogenic properties and good biocompatibility. Such properties combination make the material a good choice for components of chemical and cryomachinery as well the applications in medical and dental industries

Höganäs Ti based powders are produced via tungstenfree and crucible free manufacturing process, which excludes risk of heavy metal contamination in the material. High cleanliness level and good processability enables multiple recycling and therefore reducing total cost in production of Ti based components. Powder chemical composition complies with:

- >> ASTM B348
- >> ASTM F67


Scan the QR code to learn more about the forAM product line and other Höganäs products.





# **Powder properties**

Chemical composition, (typical values)		
Element	Content, %	
Ti	Balance	
Fe	≤0.08	
0	≤0.17 (0.09)	
С	≤0.03	
N	≤0.03	
н	≤0.01	

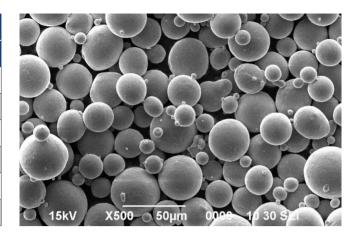

Typical powder properties		
Nominal particle range	15-53 µm	MPIF05, ASTM B214, ISO4497
Hall flow	40 s/50g	MPIF03, ASTM B213, ISO4490
Apparent density	2.34 g/cm <sup>3</sup>	MPIF04, ASTM B212, ISO3923/1


## **Mechanical properties**

Surface condition is machined		
Heat treatment	HT700 <sup>(1)</sup>	
Printed in Z-direction – Build direction		
UTS (MPa)	425	
YS (MPa)	320	
Elongation (%)	36	
IE notch in Y direction (J)	190	

Heat treatment	HT700 <sup>(1)</sup>	
Printed in X/Y-direction – Perpendicular		
UTS (MPa)	400	
YS (MPa)	280	
Elongation (%)	34	
Hardness (HV10)	130	

(1) HT700 – Stress relieved at 700 °C in vacuum for 2h, cooled in Ar atmosphere.





Etched - Stress Relived X/Y direction

## Standard packaging:

Powders are packed in 25 kg steel drums with polymer liner filled with Ar.